

pH- and Facet-Dependent Surface Chemistry of TiO₂ in Aqueous Environment from First Principles

Farahnaz Maleki, Giovanni Di Liberto,* and Gianfranco Pacchioni

Cite This: *ACS Appl. Mater. Interfaces* 2023, 15, 11216–11224

Read Online

ACCESS |


Metrics & More

Article Recommendations

Supporting Information

ABSTRACT: TiO₂ is a relevant catalytic material, and its chemistry in aqueous environment is a challenging aspect to address. Also, the morphology of TiO₂ particles at the nanoscale is often complex, spanning from faceted to spherical. In this work, we study the pH- and facet-dependent surface chemistry of TiO₂/water interfaces by performing *ab initio* molecular dynamics simulations with the grand canonical formulation of species in solution. We first determined the acid–base equilibrium constants at the interface, which allows us to estimate the pH at the point of zero charge, an important experimental observable. Then, based on simulated equilibrium constants, we predict the amount of H⁺, OH[−], and adsorbed H₂O species present on the surfaces as a function of the pH, a relevant aspect for water splitting semi-reactions. We approximated the complex morphology of TiO₂ particles by considering the rutile (110) and (011), and anatase (101), (001), and (100) surfaces.

KEYWORDS: DFT, pH dependence, *ab initio* molecular dynamics, solid/water interface, TiO₂

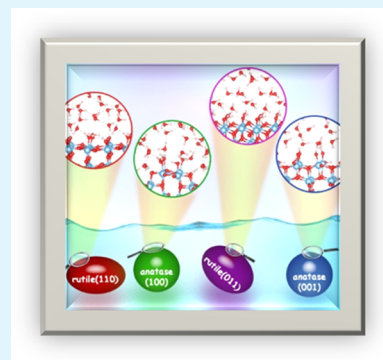

1. INTRODUCTION

The description of the nature of the oxide/water interface is a relevant topic for photocatalysis, geochemistry, and materials science in general.¹ Considering that most applications are done in aqueous environment, the fundamental understanding of how water interacts with the surface of a material is of fundamental importance and opens the way toward several applications. Several studies are devoted to the characterization of the nature of water on a catalytic material and in particular on oxide surfaces. Indeed, the local structure of water molecules can be very different from that of bulk water, and H₂O can either adsorb molecularly, or it can dissociate on the surface sites.² In addition, the interaction of a surface with water can stabilize the system or induce dissolution/degradation processes.

Once established how water interacts with a surface, an aspect of equal importance is the accurate description of acid–base equilibria since this has various implications ranging from chemical biology to geochemistry.³ For instance, in the field of catalysis, the measure of the acid–base equilibria at solid/water interfaces allows one to access very important information as the concentration of H⁺, OH[−], and adsorbed H₂O species at a surface as a function of the pH.⁴ At the same time, the estimate of equilibrium constants allows one to provide a measure of the proton transfer process, attracting attention from both experimental and theoretical chemists.^{5,6}

A relevant experimental observable in this respect is the point of zero charge (PZC),⁷ corresponding to the pH at which the concentration of H⁺ on the surface equals that of OH[−]. This quantity can be obtained once the equilibrium constants at the solid/water interface are known.⁸ Given the intrinsic atomistic

nature of problem, the quantum mechanical treatment of solid/water interface is needed. Interestingly, the prediction of the pH_{PZC} creates a direct link between the atomistic nature and macroscopic behavior of a system.

Several theoretical methodologies can be invoked to predict the equilibrium constants and pH_{PZC}.^{8–10} One of these methodologies has been proposed by Pasquarello and co-workers and is based on the grand canonical formulation of species in solution, where the nature of the solid/water interfaces and equilibrium constants can be obtained through *ab initio* molecular dynamics simulations (AIMD).⁸ The state-of-the-art methodology to approximate the electronic energy is based on density functional theory (DFT).¹¹

A widely applied and studied material is titanium dioxide mainly because of its manifold applications areas, ranging from photocatalysis to paintings. TiO₂ is mainly present in three different polymorphs, anatase, rutile, and brookite.¹² The first two are of primary importance in catalysis, and their catalytic activity can be tailored by properly engineering the exposed surfaces.^{13–15} The latter, brookite, is usually less stable, but it was successfully interfaced with anatase finding an interesting photocatalytic activity.¹⁶ TiO₂ is a challenging system given the

Received: October 26, 2022

Accepted: February 2, 2023

Published: February 14, 2023



possibility to grow different polymorphs and the tendency to interact with water.^{17–19} This can have various implications and important studies have been dedicated to understand the reactivity of water with different TiO₂ surfaces.^{20–22} For instance, it has been observed that the dissociation of water is more likely to occur on the anatase (001) surface, rather than the more stable (101) one.²³ At the same time, the rutile (110) surface mainly forms stable adducts of physisorbed water molecules.²⁴

In this work, we investigate the pH-dependent surface chemistry of TiO₂ nanoparticles in an aqueous environment. Given the complex morphology of TiO₂ particles that can range from faceted to spherical shape,¹⁸ we adopt a simplified framework considering the most relevant surfaces. More specifically, we simulate stable surfaces of anatase and rutile that can reasonably approximate the thermodynamic behavior of a particle, and we consider less stable surfaces to account for reactive sites. We do not consider extended defects such as kinks and steps, although they can impact the surface chemistry. We consider the (110) and (011) surfaces of rutile, two relevant and exposed surfaces of real titania particles. The (110) surface is the most stable one and the most important in Wulff crystal,²⁵ but also the less stable (011) one is considered to be relevant.²⁶ Moving to anatase, we considered the anatase (001) surface that contributes to the Wulff nanoparticle shape together with the (101) one.²⁷ For anatase (101), we use results from our previous work.⁹ Finally, we will account for the (100) anatase surface that can be exposed by particles under certain synthetic conditions.²⁸

We will show that the different behavior of water with various TiO₂ surfaces has important implications on the pH-dependent surface chemistry, and on the availability of charged species that in turn could have implications for the reactivity of nanoparticles. Rutile (110) and (011) surfaces exhibit significant changes in reactivity with water, being water dissociation more favorable on the (011) than on the (110), and also the acid–base equilibria are very different. Similarly, anatase (001) induces water dissociation more easily than the (101) surface. The consequence is that charged species such as H⁺ and OH[−] are more likely to be present in a large pH window on the (001) than on the (101) facet. Finally, the pH-dependent surface chemistry of anatase (100) reminds that of anatase (101).

In summary, atomistic simulations of different TiO₂ surfaces in aqueous environment indicate that water interactions range from molecular to dissociative adsorption, and the acid–base equilibria is largely affected by the nature of the different surfaces. This strongly impacts the amount of available species at the surface, with relevant implications in catalytic processes. This study also shows the importance of controlling the morphology and surface exposure of a catalyst's oxide nanoparticle.

2. COMPUTATIONAL DETAILS

The calculations have been performed using the plane-wave-based VASP code.^{29,30} The Perdew–Burke–Ernzerhof (PBE) exchange–correlation functional was adopted.³¹ The projector augmented wave (PAW) approach has been used for the treatment of core electrons,³² and valence electrons have been described with plane waves expanded with a cutoff of 400 eV. Each self-consistent field electronic energy cycle was considered converged by imposing a threshold of 10^{−5} eV. Dispersion forces have been considered according to the Grimme's D3 parametrization scheme.³³ Since PBE tends to underestimate the semiconducting behavior of TiO₂, we adopted the PBE + *U*

approach with a working Hubbard *U* term for Ti (3*d*) states equal to 3.3 eV.³⁴ *U* is usually chosen to improve the estimate of some quantity, such as the electronic structure. However, the choice of the *U* parameter can affect other quantities, and therefore the approach is not free from issues.³⁵ At the same time, PBE also underestimates the highest occupied molecular orbital–lowest unoccupied molecular orbital (HOMO–LUMO) gap of water, which could affect the accuracy if one is interested in reproducing its insulating behavior.^{36,37} Also, PBE is not exceptional in OH binding.^{38–40} In this case, one should invoke hybrid functionals.^{11,41} Therefore, the choice of the functional is not trivial since one should adopt an approach sufficiently reliable for both the material and water, which does not result in too demanding calculations. Nonhybrid functionals, including PBE, were shown sufficiently reliable in providing estimates of the pH dependence of the surface chemistry of materials, and thus the choice of the DFT functional can be considered acceptable in this respect.^{8,9} Trajectories were propagated for 5 ps after two 2 ps of equilibration. The temperature has been set to 350 K, which guarantees a frank diffusive motion of liquid water,⁸ and controlled by the Nosé–Hoover thermostat.^{42,43}

We fully optimized the bulk structure of rutile and anatase starting from the available experimental values using a tight sampling of reciprocal space.¹² We then designed surface models and optimized the atomic coordinates. We considered the most relevant rutile low-index surfaces, (110) and (011), which are relevant in rutile nanoparticles.²⁵ Moving to anatase, we simulated the reactive (001) surface,^{27,44} and the (100) surface that gained attention over the past few years because of its relative stability and high catalytic activity over specific reactions.⁴⁵ The most stable anatase surface is the (101) one.⁴⁶ Results on this system have been taken from our previous work for comparison.⁹ We report in Table 1 the structural

Table 1. Lattice Vectors, Thickness, and Surface Energy of Rutile (110), Rutile (011), Anatase (001), and Anatase (100) Models^{a,54}

	<i>a</i> /Å	<i>b</i> /Å	<i>d</i> /nm	<i>E_s</i> /J m ^{−2}
rutile (110)	2.999 (2.958)	6.552 (6.497)	1.6	1.66
rutile (011)	4.633 (4.593)	5.519 (5.463)	1.3	1.71
anatase (001)	3.852 (3.785)	3.852 (3.785)	1.4	0.93
anatase (100)	3.852 (3.785)	9.538 (9.514)	1.2	1.22

^aExperimental numbers are reported in parentheses.

parameters of the optimized clean surfaces. The quantities compare well with the experimental ones.^{45,47–49} Thickness of the surface model is an important parameter to account for to provide reliable estimates, and it has been discussed in the past.⁵⁰ In general, one should adopt a sufficiently thick model to provide reasonably converged surface properties, as the surface energy. For instance, in the case of rutile (110), previous studies showed that at least a five-layer-thick model is necessary, the same adopted here.^{51–53}

Finally, we generated supercells and interfaced them with water. A water box with a thickness of about 2 nm was created and was filled with a number of water molecules sufficient to guarantee a density of about 1 g·cm^{−3}. To create the interface, one needs to find a compromise between computational effort and size of the simulation cells to maximize the degrees of freedom, including the number of possible adsorption sites. Based on previous works,^{8,55} we generated the following models.

More specifically, a 3×1 rutile (110) supercell was interfaced, including 36 water molecules, resulting in 198 atoms in the simulation cell. A 2×1 rutile (011)/water model was created, made by 180 atoms in the simulation box, of which 36 water molecules. A 2×2 TiO₂ (001) supercell was considered (186 atoms), with 38 water molecules. A 2×1 TiO₂ (100) surface has been put in contact with the water box containing 45 water molecules and resulting in 219 atoms in the simulation cell. In each case, the starting configuration of the water box was containing seven water layers. The sampling of the reciprocal space in this case has been done to the gamma point due to the size of the simulation cells, after checking that this is an acceptable choice.⁵⁶ We evolved two trajectories for each system. In the first one, the starting configuration is characterized by molecular adsorption of water, with intact water molecules adsorbed on surface Ti sites. In the second, we considered dissociated water molecules, where OH species are adsorbed on Ti sites, and H atoms are adsorbed on surface oxygen atoms.⁸

Also in the choice of the propagation time, one must find a compromise between accuracy and computational effort. The calculated acidic constants in eqs 4 and 5 are evaluated from quantities obtained from averages along the AIMD trajectory. The error has been evaluated by means of the blocking analysis as done in previous studies.^{36,37,57} Within our simulation time, the error is always of about 0.1 eV, which is of the same order of accuracy of the whole methodology.⁸ Also, previous studies showed that such a propagation time allows us to reproduce the experimental point of zero charge of several oxides, such as BiVO₄, MgO, anatase TiO₂, and γ -Al₂O₃.^{8,9} Because of the aforementioned reasons, the propagation time can be considered sufficient to extract reliable information on the surface chemistry. This evidence agrees with previous studies on solid/water interfaces based on AIMD trajectories, based on propagation times of about 4–8 ps.^{51,55,58,59} We must stress, however, that about 1 order of magnitude larger propagation times would be necessary for a full statistical sampling.⁴¹ Moreover, the fact that 5 ps can be considered sufficient for this specific purpose does not imply that this is enough to properly reproduce other aspects of surface chemistry. Seminal works on rutile (110)/water interfaces showed that the full treatment of the system in aqueous solution requires us to propagate trajectories of about 25 ps.^{52,53}

After a propagation time of 5 ps, the two trajectories of rutile (110), rutile (011), and anatase (001) lead to very similar dissociation fractions. The only exception is represented by anatase (100) for which we found that after 5 ps two different pictures are possible and the energies are almost comparable. In the first case, we found both adsorbed and dissociated water molecules at the surface, while in the second case, a fully dissociated water layer is present. Further studies are planned for this system to better characterize these features. In the present work, we decided to proceed with the propagation of charged trajectories from the first case since it contains both molecularly and dissociated water molecules. Figure 1 shows a snapshot of the rutile (110)/water, rutile (011)/water, anatase (001)/water, and anatase (100)/water interfaces.

The main working equations to determine acidic constants and point of zero charge are reported below. More details can be found in the Supporting Information (SI) and in refs 8 and 9. In this study, we adopt the formulation proposed by Pasquarello and co-workers, based on the grand canonical formulation of species in solution; see eqs S1–S3.^{8,36} In particular, one can



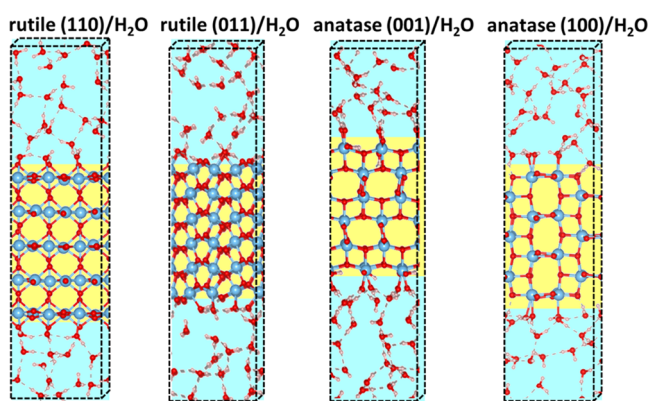


Figure 1. Snapshot of rutile (110)/water, rutile (011)/water, anatase (001)/water, and anatase (100)/water interfaces.

propagate ab initio molecular dynamics AIMD trajectories of neutral TiO₂/water interface, and the same by adding or removing an extra proton at the interface.⁸ This allows us to describe acid–base reactions described below. Each AIMD trajectory is propagated with a constant number of particles. A uniform charged background was added to compensate the extra charge. We neglected finite size effects, which are often very small (0.01–0.02 eV) for water and materials with a significant dielectric constant.⁴¹ It must be said that a change in the charge state of a system can imply a shift in the potential of electrodes, with possible consequences when studying electrocatalytic processes.⁶⁰ On the surface of TiO₂, a proton from water can be attached to a surface oxygen atom (O_sH⁺), and a water molecule can adsorb on a titanium one (H₂O_{Ti}). The acid–base equilibria can then be written according to the following reactions



Described by the corresponding equilibrium constants

$$k_a(\text{O}_s\text{H}^+) = \frac{[\text{O}_s][\text{H}_3\text{O}^+]}{[\text{O}_s\text{H}^+]} = k_a^I \quad (1)$$

$$k_a(\text{H}_2\text{O}_{\text{Ti}}) = \frac{[\text{OH}_{\text{Ti}}^-][\text{H}_3\text{O}^+]}{[\text{H}_2\text{O}_{\text{Ti}}]} = k_a^{II} \quad (2)$$

If we label the total number of exposed titanium and oxygen sites as C_{Ti} and C_{O} , the pH corresponding to PZC (pH_{PZC}) is equal to⁸

$$\text{pH}_{\text{PZC}} = \frac{\text{p}K_a(\text{O}_s\text{H}^+) + \text{p}K_a(\text{H}_2\text{O}_{\text{Ti}})}{2} - \frac{1}{2} \log \left(\frac{C_{\text{Ti}}}{C_{\text{O}}} \right) \quad (3)$$

The derivation of the working equations for equilibrium constants is reported in eqs S4–S14. They can be calculated as

$$\begin{aligned} \text{p}K_a(\text{O}_s\text{H}^+) = & \frac{[\Delta_{\text{dp}}A_{\text{O}_s\text{H}^+} - \Delta_{\text{dp}}A_{\text{H}^+}]}{k_b T \ln 10} \\ & + \frac{[-\Delta_{\text{zp}}E_{\text{O}_s\text{H}^+} + \Delta_{\text{zp}}E_{\text{H}^+}]}{k_b T \ln 10} \\ & + \frac{[V_w(\text{int}) - V_w]}{k_b T \ln 10} - \log c_0 \end{aligned} \quad (4)$$

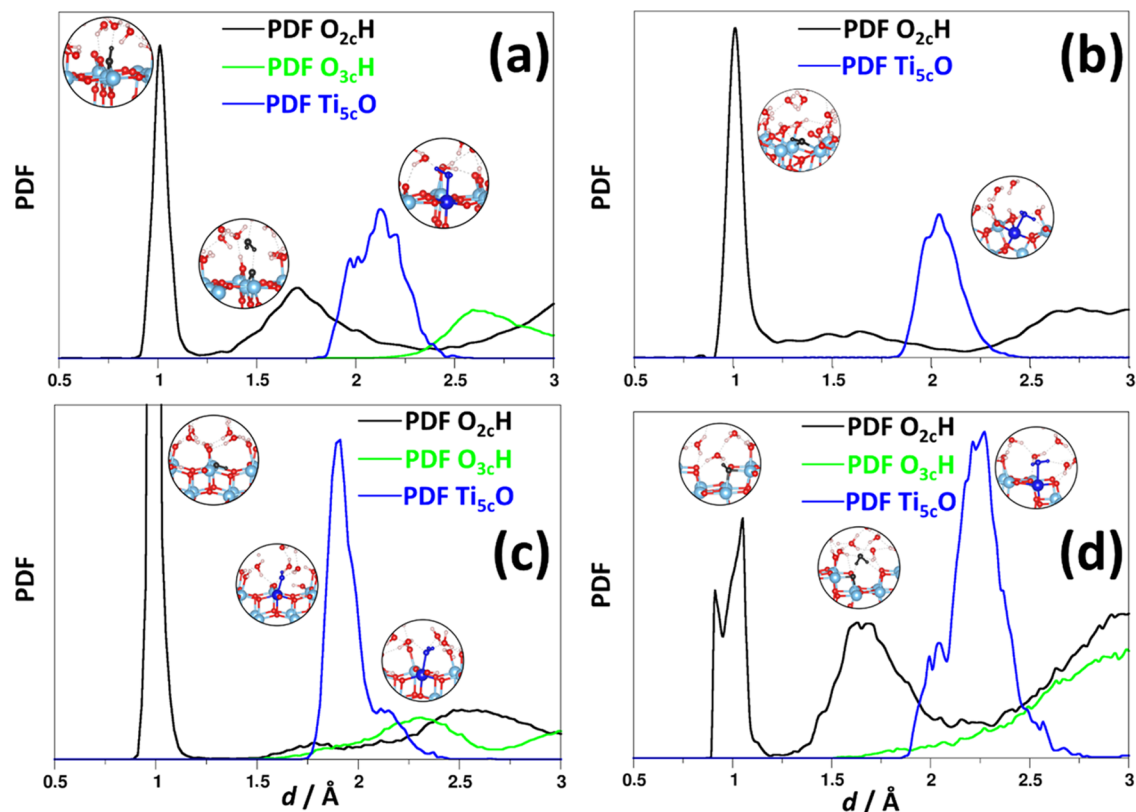


Figure 2. Calculated pair distribution function (PDF) between O_{2c} and H atoms (black solid line), O_{3c} and H atoms (green solid line), and surface Ti and O atoms of water (blue solid line) for TiO_2 /water interfaces. (a–d) Rutile (110), rutile (011), anatase (001), and anatase (100), respectively.

$$\begin{aligned}
 pK_a(H_2O_{Ti}) = & \frac{[\Delta_{dp}A_{(H_2O)_{Ti}} - \Delta_{dp}A_{H^+}]}{k_b T \ln 10} \\
 & + \frac{[-\Delta_{zp}E_{(H_2O)_{Ti}} + \Delta_{zp}E_{H^+}]}{k_b T \ln 10} \\
 & + \frac{[V_w(int) - V_w]}{k_b T \ln 10} - \log c_0
 \end{aligned} \quad (5)$$

Each term of the equations is averaged along AIMD simulation of TiO_2 /water interfaces. The first term is the integral for the deprotonation of an adsorbed proton of the surface $\Delta_{dp}A_{O_{2c}H^+}$, of an adsorbed water molecule on a surface $\Delta_{dp}A_{(H_2O)_{Ti}}$, with respect to the same property evaluated in acidic bulk water $\Delta_{dp}A_{H^+}$. These integrals are obtained by propagating AIMD simulations of a neutral TiO_2 /water interface, and the same having an extra proton and a hydroxyl ion adsorbed on the surface.^{8,9} The second term is related to the zero-point energy correction, and the third term is associated with the difference between the macroscopic averaged electrostatic potential on the water side of the neutral TiO_2 /water interface and the same of bulk water.^{8,9} c_0 is the concentration of water molecules in water solution $c_0 = \frac{1000 \text{ g}}{18 \text{ g/mol}}$.

The same approach can be used to calculate the relative stability of molecular and dissociative adsorption of water molecules.^{8,9} This is derived in the SI, eqs S16 and S17. Indeed, we can estimate the energy (ΔA_d) to dissociate a molecularly adsorbed water molecule as

$$\Delta A_d = k_b T \ln 10 [pk_a^{II} - pk_a^I] \quad (6)$$

Such an approach is somewhat related to the very successful computational hydrogen electrode (CHE) method of Norskov and co-workers,^{61,62} where the dissociation free energy of water can be obtained from the calculation of minimum-energy structures followed by the inclusion of thermodynamic correction. The current methodology already accounts for the fluxional behavior of water, resulting in the presence of several local minima very close in energy. Once evaluated the acidic constants and the point of zero charge, it is possible to study the amount of charged species and free surface sites as a function of the pH. Full details and derivation are reported in the SI and in ref 9. Indeed, the molar fraction of the species on the surface is

$$\begin{aligned}
 \chi_{O_{2c}H^+} &= \frac{10^{-pH}}{k_a^I + 10^{-pH}} \\
 \chi_{O_{3c}} &= \frac{k_a^I}{k_a^I + 10^{-pH}} \\
 \chi_{H_2O_{Ti}} &= \frac{10^{-pH}}{k_a^{II} + 10^{-pH}} \\
 \chi_{OH_{Ti}^-} &= \frac{k_a^{II}}{k_a^{II} + 10^{-pH}}
 \end{aligned} \quad (7)$$

3. RESULTS AND DISCUSSION

3.1. Neutral TiO_2 /H₂O Interfaces. We start from the analysis of the rutile (110)/H₂O interface. After 5 ps, the fraction of dissociated water molecules on the surface reaches a stable value of about 25%. Figure 2 shows the pair distribution

Table 2. Calculated Deprotonation Integrals with respect to $\Delta_{\text{dp}}A_{\text{H}^+}$, Equilibrium Constants (pK_{a}^{I} , $pK_{\text{a}}^{\text{II}}$), and pH_{PZC} Compared with Available Experimental Values for Rutile (110), Anatase (001), and Anatase (100) Surfaces^a

system	$\Delta_{\text{dp}}A_{\text{O}_2\text{H}^+}/\text{eV}$	$\Delta_{\text{dp}}A_{\text{H}_2\text{O}_2}/\text{eV}$	pK_{a}^{I}	$pK_{\text{a}}^{\text{II}}$	pH_{PZC}	$\text{pH}_{\text{PZC}}^{\text{EXP7,64,66}}$
rutile (110)	-0.64	-0.17	1.45	9.02	5.39	$\sim 6^b$
rutile (011)	-0.52	-0.33	2.60	5.65	4.28	
anatase (001)	-0.72	-0.40	3.40	8.05	5.88	
anatase (100)	-1.15	-0.32	1.24	12.50	7.02	
anatase (101)	-1.12	-0.62	2.33	9.27	5.95	$\sim 6^b$

^aResults for anatase (101) taken from ref 9. ^bThe experimental values are averaged over the various surfaces exposed. Here, it is associated with the most stable surface of the TiO_2 polymorph.

function (PDF) between surface atoms and water. The peak at 0.99 Å characterizes the formation of $\text{cO}_s\text{-H}$ bonds, due to water chemisorption. The calculated coordination number is 0.25, in agreement with the fraction of water dissociated on the surface. The coordination number is evaluated by integrating the PDF.⁶³ A second peak at 1.7 Å is due to hydrogen bonding between the O_{2c} atoms and water molecules. The calculated coordination number is 0.66; therefore, a significantly strong network of hydrogen bonding forms between rutile (110) and water. O_{3c} atoms on the surface are nearly inert, as evinced by the large distances shown in Figure 2a. The PDF between titanium atoms and oxygen species shows a peak at 2.1 Å due to the interaction with adsorbed H_2O and OH^- species arising from water dissociation. The calculated coordination number is one; therefore, on average, each titanium atom is covered. The first layer of water molecules on the surface arranges in dimers, as already reported, with a typical O–O distance of 3.0 Å.²⁴ The calculated free energy of water dissociation is 0.53 eV, indicating that the chemisorption process is endergonic. This number is comparable to that of anatase (101)/ H_2O interface, 0.48 eV.⁹

The rutile (011)/water interface displays large changes with respect to the (110)/water one. Indeed, after 5 ps, the dissociation fraction is significantly larger, about 50%, as also suggested by the calculated coordination number between O_{2c} and H. The corresponding PDF is reported in Figure 2b. Consistently, the calculated water dissociation energy is 0.21 eV, about half of that of rutile (110). Hydrogen bonding is present, as evinced by the broad signal at 1.7 Å, where each O_{2c} atom contributes to 0.5 hydrogen bonds. Similar to the (110) surface, each Ti_{5c} atom is on average interacting with a OH^- or a H_2O species, with a $\text{Ti}_{5c}\text{-O}$ distance of 2.1 Å.

Moving to the anatase surfaces, the analysis of TiO_2 (001)/water trajectory indicates that there is a larger tendency for water dissociation.^{20,23} Indeed, after 5 ps, the dissociation fraction is about 75%, due to the higher reactivity of this surface. Indeed, the calculated dissociation free energy is 0.32 eV, much lower than for rutile (110) and anatase (101). In this latter case, it has been shown that water tends to adsorb molecularly on the surface.²² Figure 2c reports the calculated PDFs, where it is possible to identify the main $\text{O}_{2c}\text{-H}$ peak at about 0.99 Å, with an average coordination number of 0.75. The peak at 1.91 Å is associated with the interaction between Ti_{5c} atoms and OH^- ions arising from water dissociation, with the same coordination number, 0.75, confirming the calculated dissociation fraction. The small shoulder at 2.1 Å is attributed to the small number of water molecules on the surface, and indeed the average coordination number is 0.25. All titanium atoms on the surface are interacting on average with one water molecule. The peak at 1.7 Å is due to hydrogen bonding between O_{2c} and water, and the calculated coordination number is 0.2. Interestingly, while there is a larger dissociation of water molecules on the anatase

(001) surface than on the rutile (110), $\alpha = 0.75$ and $\alpha = 0.25$, respectively, there is a consequent decrease of the available sites for H-bonding, which results in a much smaller coordination number, 0.2 and 0.66 for anatase (001) and rutile (110), respectively.

We now analyze the anatase (100)/water interface. In this case, the most likely interaction is physisorption, since the dissociation fraction is low, 12%, comparable to that of anatase (101),⁹ at variance to anatase (001). Indeed, the calculated dissociation energy is higher than that of anatase (001), $\Delta A = 0.78$ eV. As already mentioned, a conclusive picture of water adsorption on solid surfaces would require much longer simulation times, but this aspect goes beyond the purpose of this study. In fact, further work is needed to fully elucidate the anatase (100)/water interface. Figure 2d reports the analysis of the PDF, where the typical $\text{O}_{2c}\text{-H}$, $\text{Ti}_{5c}\text{-OH}$, and $\text{Ti}_{5c}\text{-H}_2\text{O}$ distances are nearly the same as of anatase (001). Interestingly, the amount of hydrogen bonding between O_{2c} atoms and water is quite high, about 0.5, which is comparable to that of rutile (110).

3.2. Acidity of TiO_2 Surfaces. As mentioned above, the propagation of two trajectories, one including an extra proton attached to the surface, and the second that includes a hydroxyl species, allow us to evaluate the acidity of the different surface sites and the point of zero charge. In addition, starting from the calculated pK_{a} 's, it is possible to derive the amounts of H^+ , OH^- , and H_2O species present on the surfaces. Table 2 reports the calculated equilibrium constants and points of zero charge. Tables S1 and S2 report the calculated deprotonation energies and zero-point energy corrections. For the most stable surfaces of rutile and anatase, the (110) and (101), respectively, we compute a pH_{PZC} of 5.39 and 5.95 (see Table 2), indicating a slightly acidic behavior.⁶⁴ Both values are close to the reported experimental estimates of a pH_{PZC} about 6. Notice, however, that the fact that the pH_{PZC} of rutile is about 0.5 pH units lower than that of anatase surfaces finds support in some experimental observations.⁶⁵ Of course, what is measured experimentally is an average of the behavior of the variously exposed facets in TiO_2 nanoparticles, and this in turn depends on the preparation of the sample. With our calculations, on the contrary, we can provide a detailed analysis of the dependence of the pH_{PZC} on the exposed surface.

The point of zero charge of rutile (011), 4.28, is significantly lower than that of the most stable (110) surface, 5.39, indicating a stronger acidity of this surface. Moving to the anatase (001)/water interface, the calculated point of zero charge is 5.88, very similar to that of rutile and in agreement with that measured for anatase crystals.^{7,66} Interestingly, the behavior of the other anatase surface, (100), is substantially different, as reported experimentally.⁶⁷ Indeed, the calculated point of zero charge,

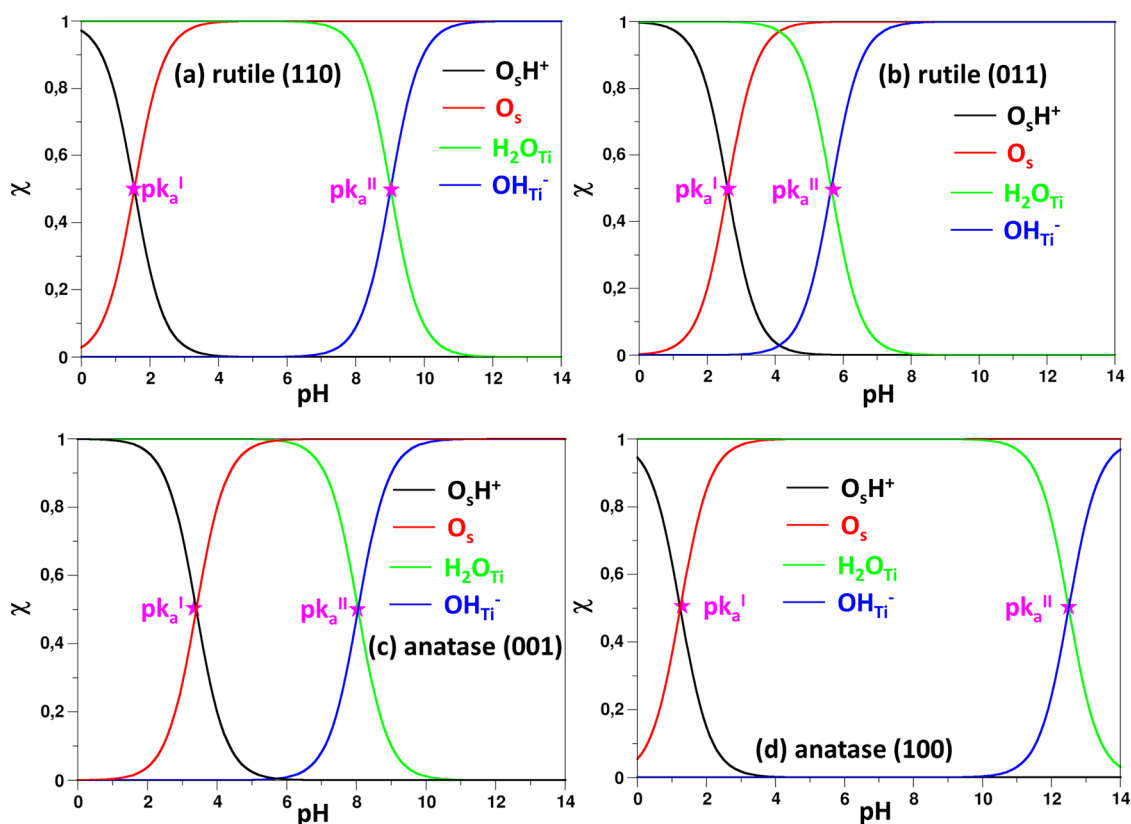


Figure 3. Speciation of adsorbed water (H_2O), free surface oxygen sites (O_s), and H^+ and OH^- species as a function of pH on the surface of (a) rutile (110), (b) rutile (011), (c) anatase (001), and (d) anatase (100).

7.02, is considerably higher than that of the other surfaces considered.

The different acidic behavior of the surface models considered has a direct implication on the amount of species present on the surfaces, a relevant aspect for reactions such as water splitting.^{68,69}

Figure 3 shows the trend of molar fractions of surface sites as a function of pH. Figure 4 depicts the pH window at which the species are available of the surface. A threshold value of 10% was adopted.⁹ The speciation diagrams are obtained from eqs S20 and S21 and are based on a post-process analysis depending on the calculated acidic constants.⁹ Therefore, the estimates should be taken with some care in analyzing absolute numbers, while they can provide some useful information when looking at trends and doing comparisons.

We see that for the rutile(110)/water interface, H^+ ions are present on the surface only at a quite low pH, below 2.5, while at higher pH values, the surface oxygen atoms are expected to be free. At the same time, OH^- ions display larger stability since they are present on the surface at $\text{pH} > 8$. Given the large acidity of rutile (011), OH^- ions are found in a large pH window. Moving to the anatase (001)/water model, although the pH_{PZC} is quite similar to that of rutile (110), the different pK_a 's imply a very different pH-dependent behavior. Water dissociation is more favorable on this surface, and indeed both H^+ and OH^- species are likely to be present on the surface, for $\text{pH} < 4.5$ and $\text{pH} > 7.0$, respectively. The different surface chemistry is even more evident when comparing anatase (100) and (001) surfaces. H^+ and OH^- species are unlikely to be present on the first surface, according to the energy cost to dissociate water molecules on the surface. H^+ becomes abundant only at $\text{pH} <$

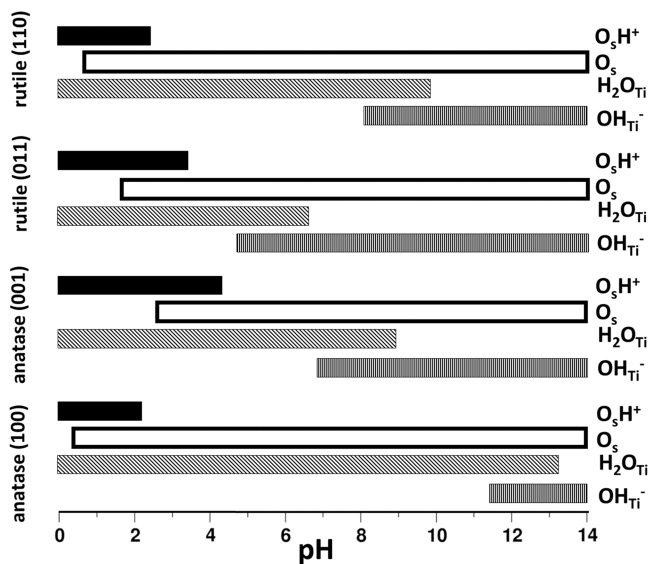


Figure 4. pH windows at which the H^+ , O_s , H_2O , and OH^- species are present on the surface. A threshold molar fraction of 10% has been adopted.

2.5, and OH^- for $\text{pH} > 11.5$. At the same time, the window where water molecules dominate is the largest among the four models since H_2O is present on the surface for $\text{pH} < 13$. The pH-dependent behavior of the different facets can have implications for the catalytic activity. For instance, anatase crystals made by anatase/rutile junctions are found to be active for photocatalytic hydrogen production. This is mainly attributed to the improved charge carriers separation due to a favorable alignment of the

band edges, where electrons are promoted to migrate toward the anatase (101) facet and holes toward the rutile (110) one.⁷⁰ Our results indicate that the presence of H⁺ is more likely to occur on anatase (101) according to Table 2, which is an additional important requirement for high activity in hydrogen production.

4. CONCLUSIONS

In this work, we investigated the pH- and facet-dependent surface chemistry of TiO₂ in aqueous environment by means of ab initio molecular dynamics simulations. We considered rutile (110), rutile (011), anatase (001), anatase (100), and anatase (101) surfaces. We first looked at the nature of the interaction of water and the surface, finding that the tendency toward chemisorption is strongly surface-sensitive. Water is preferentially adsorbed molecularly on rutile (110) and anatase (100), and it is more likely to dissociate on rutile (011) and anatase (001). The fraction of dissociated molecules correlates significantly with the computed dissociation energy on the surface. We used the grand canonical formulation of species in solution to estimate the acid–base equilibrium constants at the TiO₂/water interface. This required the simulation of additional trajectories including explicitly an extra proton and a hydroxyl group in the supercell simulating the interface. The calculated constants were used to estimate the pH of point of zero charge, an important experimental quantity. Even in this case, the results indicate that the chemistry of water on titania is surface-sensitive. The pH_{PZC} of rutile surfaces is slightly lower than that of anatase, in line with experimental observations.⁶⁵ The differences in equilibrium constants at the surface have relevant implications for the amount of H⁺, OH⁻, and H₂O species that can be present on the surface as a function of pH. Further work will be dedicated to expanding the model to include more realistic 3D nanoparticles and extended defects such as steps and kinks.

■ ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsami.2c19273>.

Details and derivation of the methodology (Tables S1 and S2) (PDF)

■ AUTHOR INFORMATION

Corresponding Author

Giovanni Di Liberto – Dipartimento di Scienza dei Materiali,
Università di Milano-Bicocca, 20125 Milano, Italy;
orcid.org/0000-0003-4289-2732;
Email: giovanni.diliberto@unimib.it

Authors

Farahnaz Maleki – Dipartimento di Scienza dei Materiali,
Università di Milano-Bicocca, 20125 Milano, Italy
Gianfranco Pacchioni – Dipartimento di Scienza dei Materiali,
Università di Milano-Bicocca, 20125 Milano, Italy;
orcid.org/0000-0002-4749-0751

Complete contact information is available at:
<https://pubs.acs.org/doi/10.1021/acsami.2c19273>

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

The authors acknowledge the financial support Cariplo Foundation. Access to the CINECA supercomputing resources was granted via ISCRAB. The authors also thank the COST Action 18234 supported by COST (European Cooperation in Science and Technology).

■ REFERENCES

- (1) Björneholm, O.; Hansen, M. H.; Hodgson, A.; Liu, L.-M.; Limmer, D. T.; Michaelides, A.; Pedevilla, P.; Rossmeisl, J.; Shen, H.; Tocci, G.; et al. Water at Interfaces. *Chem. Rev.* **2016**, *116*, 7698–7726.
- (2) Laporte, S.; Finocchi, F.; Paulatto, L.; Blanchard, M.; Balan, E.; Guyot, F.; Saitta, A. M. Strong Electric Fields at a Prototypical Oxide/Water Interface Probed by Ab Initio Molecular Dynamics: MgO(001). *Phys. Chem. Chem. Phys.* **2015**, *17*, 20382–20390.
- (3) Donaldson, M. A.; Bish, D. L.; Raff, J. D. Soil Surface Acidity Plays a Determining Role in the Atmospheric–Terrestrial Exchange of Nitrous Acid. *Proc. Natl. Acad. Sci. U.S.A.* **2014**, *111*, 18472–18477.
- (4) Pham, T. A.; Ping, Y.; Galli, G. Modelling Heterogeneous Interfaces for Solar Water Splitting. *Nat. Mater.* **2017**, *16*, 401–408.
- (5) Kisch, H. Semiconductor Photocatalysis for Chemoselective Radical Coupling Reactions. *Acc. Chem. Res.* **2017**, *50*, 1002–1010.
- (6) Gaigeot, M.-P.; Sprik, M.; Sulpizi, M. Oxide/Water Interfaces: How the Surface Chemistry Modifies Interfacial Water Properties. *J. Phys.: Condens. Matter* **2012**, *24*, No. 124106.
- (7) Bourikas, K.; Vakros, J.; Kordulis, C.; Lycourghiotis, A. Potentiometric Mass Titrations: Experimental and Theoretical Establishment of a New Technique for Determining the Point of Zero Charge (PZC) of Metal (Hydr)Oxides. *J. Phys. Chem. B* **2003**, *107*, 9441–9451.
- (8) Ambrosio, F.; Wiktor, J.; Pasquarello, A. PH-Dependent Surface Chemistry from First Principles: Application to the BiVO₄ (010)–Water Interface. *ACS Appl. Mater. Interfaces* **2018**, *10*, 10011–10021.
- (9) Di Liberto, G.; Maleki, F.; Pacchioni, G. PH Dependence of MgO, TiO₂, and γ -Al₂O₃ Surface Chemistry from First Principles. *J. Phys. Chem. C* **2022**, *126*, 10216–10223.
- (10) Tummanapelli, A. K.; Vasudevan, S. Ab Initio Molecular Dynamics Simulations of Amino Acids in Aqueous Solutions: Estimating pK_a Values from Metadynamics Sampling. *J. Phys. Chem. B* **2015**, *119*, 12249–12255.
- (11) Guo, Z.; Ambrosio, F.; Chen, W.; Gono, P.; Pasquarello, A. Alignment of Redox Levels at Semiconductor–Water Interfaces. *Chem. Mater.* **2018**, *30*, 94–111.
- (12) Wyckoff, R. W. R. *Crystal Structures*, 2nd ed.; Interscience Publishers: New York, 1963.
- (13) Hurum, D. C.; Agrios, A. G.; Gray, K. A.; Rajh, T.; Thurmaier, M. C. Explaining the Enhanced Photocatalytic Activity of Degussa P25 Mixed-Phase TiO₂ Using EPR. *J. Phys. Chem. B* **2003**, *107*, 4545–4549.
- (14) Scanlon, D. O.; Dunnill, C. W.; Buckeridge, J.; Shevlin, S. A.; Logsdail, A. J.; Woodley, S. M.; Catlow, C. R. A.; Powell, M. J.; Palgrave, R. G.; Parkin, I. P.; et al. Band Alignment of Rutile and Anatase TiO₂. *Nat. Mater.* **2013**, *12*, 798–801.
- (15) Di Liberto, G.; Tosoni, S.; Pacchioni, G. Charge Carriers Cascade in a Ternary TiO₂/TiO₂/ZnS Heterojunction: A DFT Study. *ChemCatChem* **2020**, *12*, 2097–2105.
- (16) Lo Presti, L.; Pifferi, V.; Di Liberto, G.; Cappelletti, G.; Falciola, L.; Cerrato, G.; Ceotto, M. Direct Measurement and Modeling of Spontaneous Charge Migration across Anatase–Brookite Nano-heterojunctions. *J. Mater. Chem. A* **2021**, *9*, 7782–7790.
- (17) Linsebigler, A. L.; Lu, G.; Yates, J. T. Photocatalysis on TiO₂ Surfaces: Principles, Mechanisms, and Selected Results. *Chem. Rev.* **1995**, *95*, 735–758.
- (18) Morales-García, Á.; Escatllar, A. M.; Illas, F.; Bromley, S. T. Understanding the Interplay between Size, Morphology and Energy Gap in Photoactive TiO₂ Nanoparticles. *Nanoscale* **2019**, *11*, 9032–9041.

- (19) Balajka, J.; Aschauer, U.; Mertens, S. F. L.; Selloni, A.; Schmid, M.; Diebold, U. Surface Structure of TiO₂ Rutile (011) Exposed to Liquid Water. *J. Phys. Chem. C* **2017**, *121*, 26424–26431.
- (20) Hosseinpour, S.; Tang, F.; Wang, F.; Livingstone, R. A.; Schlegel, S. J.; Ohto, T.; Bonn, M.; Nagata, Y.; Backus, E. H. G. Chemisorbed and Physisorbed Water at the TiO₂/Water Interface. *J. Phys. Chem. Lett.* **2017**, *8*, 2195–2199.
- (21) Andrade, M. F. C.; Ko, H.-Y.; Zhang, L.; Car, R.; Selloni, A. Free Energy of Proton Transfer at the Water–TiO₂ Interface from Ab Initio Deep Potential Molecular Dynamics. *Chem. Sci.* **2020**, *11*, 2335–2341.
- (22) Andrade, M. F. C.; Ko, H.-Y.; Car, R.; Selloni, A. Structure, Polarization, and Sum Frequency Generation Spectrum of Interfacial Water on Anatase TiO₂. *J. Phys. Chem. Lett.* **2018**, *9*, 6716–6721.
- (23) Sumita, M.; Hu, C.; Tateyama, Y. Interface Water on TiO₂ Anatase (101) and (001) Surfaces: First-Principles Study with TiO₂ Slabs Dipped in Bulk Water. *J. Phys. Chem. C* **2010**, *114*, 18529–18537.
- (24) Serrano, G.; Bonanni, B.; Di Giovannantonio, M.; Kosmala, T.; Schmid, M.; Diebold, U.; Di Carlo, A.; Cheng, J.; VandeVondele, J.; Wandelt, K.; Goletti, C. Molecular Ordering at the Interface Between Liquid Water and Rutile TiO₂ (110). *Adv. Mater. Interfaces* **2015**, *2*, No. 1500246.
- (25) Morgan, B. J.; Watson, G. W. A DFT+U Description of Oxygen Vacancies at the TiO₂ Rutile (110) Surface. *Surf. Sci.* **2007**, *601*, 5034–5041.
- (26) Liu, G.; Yu, J. C.; Lu, G. Q. M.; Cheng, H.-M. Crystal Facet Engineering of Semiconductor Photocatalysts: Motivations, Advances and Unique Properties. *Chem. Commun.* **2011**, *47*, No. 6763.
- (27) Selloni, A. Anatase Shows Its Reactive Side. *Nat. Mater.* **2008**, *7*, 613–615.
- (28) Li, J.; Xu, D. Tetragonal Faceted-Nanorods of Anatase TiO₂ Single Crystals with a Large Percentage of Active {100} Facets. *Chem. Commun.* **2010**, *46*, 2301–2303.
- (29) Kresse, G.; Furthmüller, J. Efficient Iterative Schemes for Ab Initio Total-Energy Calculations Using a Plane-Wave Basis Set. *Phys. Rev. B* **1996**, *54*, 11169–11186.
- (30) Kresse, G.; Hafner, J. Ab Initio Molecular Dynamics for Liquid Metals. *Phys. Rev. B* **1993**, *47*, 558–561.
- (31) Perdew, J. P.; Burke, K.; Ernzerhof, M. Generalized Gradient Approximation Made Simple. *Phys. Rev. Lett.* **1996**, *77*, 3865–3868.
- (32) Blöchl, P. E. Projector Augmented-Wave Method. *Phys. Rev. B* **1994**, *50*, 17953–17979.
- (33) Grimme, S.; Antony, J.; Ehrlich, S.; Krieg, H. A Consistent and Accurate Ab Initio Parametrization of Density Functional Dispersion Correction (DFT-D) for the 94 Elements H–Pu. *J. Chem. Phys.* **2010**, *132*, No. 154104.
- (34) Marchiori, C.; Di Liberto, G.; Soliveri, G.; Loconte, L.; Lo Presti, L.; Meroni, D.; Ceotto, M.; Oliva, C.; Cappelli, S.; Cappelletti, G.; et al. Unraveling the Cooperative Mechanism of Visible-Light Absorption in Bulk N,Nb Codoped TiO₂ powders of Nanomaterials. *J. Phys. Chem. C* **2014**, *118*, 24152–24164.
- (35) Zhao, Q.; Kulik, H. J. Stable Surfaces That Bind Too Tightly: Can Range-Separated Hybrids or DFT+U Improve Paradoxical Descriptions of Surface Chemistry? *J. Phys. Chem. Lett.* **2019**, *10*, 5090–5098.
- (36) Ambrosio, F.; Miceli, G.; Pasquarello, A. Redox Levels in Aqueous Solution: Effect of van Der Waals Interactions and Hybrid Functionals. *J. Chem. Phys.* **2015**, *143*, No. 244508.
- (37) Ambrosio, F.; Miceli, G.; Pasquarello, A. Structural, Dynamical, and Electronic Properties of Liquid Water: A Hybrid Functional Study. *J. Phys. Chem. B* **2016**, *120*, 7456–7470.
- (38) Santra, B.; Michaelides, A.; Scheffler, M. Coupled Cluster Benchmarks of Water Monomers and Dimers Extracted from Density-Functional Theory Liquid Water: The Importance of Monomer Deformations. *J. Chem. Phys.* **2009**, *131*, No. 124509.
- (39) Brémond, É.; Savarese, M.; Rega, N.; Ciofini, I.; Adamo, C. Free Energy Profiles of Proton Transfer Reactions: Density Functional Benchmark from Biased Ab Initio Dynamics. *J. Chem. Theory Comput.* **2022**, *18*, 1501–1511.
- (40) Svozil, D.; Jungwirth, P. Cluster Model for the Ionic Product of Water: Accuracy and Limitations of Common Density Functional Methods. *J. Phys. Chem. A* **2006**, *110*, 9194–9199.
- (41) Ambrosio, F.; Guo, Z.; Pasquarello, A. Absolute Energy Levels of Liquid Water. *J. Phys. Chem. Lett.* **2018**, *9*, 3212–3216.
- (42) Nosé, S. A Unified Formulation of the Constant Temperature Molecular Dynamics Methods. *J. Chem. Phys.* **1984**, *81*, 511–519.
- (43) Hoover, W. G. Canonical Dynamics: Equilibrium Phase-Space Distributions. *Phys. Rev. A* **1985**, *31*, 1695–1697.
- (44) Gong, X.-Q.; Selloni, A. Reactivity of Anatase TiO₂ Nanoparticles: The Role of the Minority (001) Surface. *J. Phys. Chem. B* **2005**, *109*, 19560–19562.
- (45) Labat, F.; Baranek, P.; Adamo, C. Structural and Electronic Properties of Selected Rutile and Anatase TiO₂ Surfaces: An Ab Initio Investigation. *J. Chem. Theory Comput.* **2008**, *4*, 341–352.
- (46) Lazzeri, M.; Vittadini, A.; Selloni, A. Structure and Energetics of Stoichiometric TiO₂ Anatase Surfaces. *Phys. Rev. B* **2001**, *63*, No. 155409.
- (47) Liberto, G.; Di; Tosoni, S.; Pacchioni, G. Role of Surface Termination in Forming Type-II Photocatalyst Heterojunctions: The Case of TiO₂/BiVO₄. *J. Phys.: Condens. Matter* **2020**, *33*, No. 075001.
- (48) Di Liberto, G.; Tosoni, S.; Illas, F.; Pacchioni, G. Nature of SrTiO₃/TiO₂ (Anatase) Heterostructure from Hybrid Density Functional Theory Calculations. *J. Chem. Phys.* **2020**, *152*, No. 184704.
- (49) Oliver, P. M.; Watson, G. W.; Kelsey, E. T.; Parker, S. C. Atomistic Simulation of the Surface Structure of the TiO₂ Polymorphs Rutile and Anatase. *J. Mater. Chem.* **1997**, *7*, 563–568.
- (50) Bredow, T.; Giordano, L.; Cinquini, F.; Pacchioni, G. Electronic Properties of Rutile <TiO₂ Ultrathin Films: Odd-Even Oscillations with the Number of Layers. *Phys. Rev. B* **2004**, *70*, No. 035419.
- (51) Gono, P.; Ambrosio, F.; Pasquarello, A. Effect of the Solvent on the Oxygen Evolution Reaction at the TiO₂–Water Interface. *J. Phys. Chem. C* **2019**, *123*, 18467–18474.
- (52) Liu, L.-M.; Zhang, C.; Thornton, G.; Michaelides, A. Structure and Dynamics of Liquid Water on Rutile TiO₂. *Phys. Rev. B* **2010**, *82*, No. 161415.
- (53) Liu, L.-M.; Zhang, C.; Thornton, G.; Michaelides, A. Reply to “Comment on ‘Structure and Dynamics of Liquid Water on Rutile TiO₂ (110)’. *Phys. Rev. B* **2012**, *85*, No. 167402.
- (54) Wyckoff, R. W. G. *Crystal Structures*; Wiley, 1963.
- (55) Wiktor, J.; Pasquarello, A. Electron and Hole Polarons at the BiVO₄–Water Interface. *ACS Appl. Mater. Interfaces* **2019**, *11*, 18423–18426.
- (56) Monkhorst, H. J.; Pack, J. D. Special Points for Brillouin-Zone Integrations. *Phys. Rev. B* **1976**, *13*, 5188–5192.
- (57) Flyvbjerg, H.; Petersen, H. G. Error Estimates on Averages of Correlated Data. *J. Chem. Phys.* **1989**, *91*, 461–466.
- (58) Kaiser, W.; Ricciarelli, D.; Mosconi, E.; Althman, A. A.; Ambrosio, F.; De Angelis, F. Stability of Tin- versus Lead-Halide Perovskites: Ab Initio Molecular Dynamics Simulations of Perovskite/Water Interfaces. *J. Phys. Chem. Lett.* **2022**, *13*, 2321–2329.
- (59) Monteiro, M. C. O.; Dattila, F.; Hagedoorn, B.; García-Muelas, R.; López, N.; Koper, M. T. M. Absence of CO₂ Electroreduction on Copper, Gold and Silver Electrodes without Metal Cations in Solution. *Nat. Catal.* **2021**, *4*, 654–662.
- (60) Cheng, T.; Wang, L.; Merinov, B. V.; Goddard, W. A. Explanation of Dramatic PH-Dependence of Hydrogen Binding on Noble Metal Electrode: Greatly Weakened Water Adsorption at High PH. *J. Am. Chem. Soc.* **2018**, *140*, 7787–7790.
- (61) Norskov, J. K.; Christensen, C. H. Toward Efficient Hydrogen Production at Surfaces. *Science* **2006**, *312*, 1322–1323.
- (62) Norskov, J. K.; Rossmeisl, J.; Logadottir, A.; Lindqvist, L.; Kitchin, J. R.; Bligaard, T.; Jónsson, H. Origin of the Overpotential for Oxygen Reduction at a Fuel-Cell Cathode. *J. Phys. Chem. B* **2004**, *108*, 17886–17892.
- (63) Caprion, D.; Schober, H. R. Structure and Relaxation in Liquid and Amorphous Selenium. *Phys. Rev. B* **2000**, *62*, 3709–3716.

(64) Kosmulski, M. Isoelectric Points and Points of Zero Charge of Metal (Hydr)Oxides: 50years after Parks' Review. *Adv. Colloid Interface Sci.* **2016**, *238*, 1–61.

(65) Kosmulski, M. The Significance of the Difference in the Point of Zero Charge between Rutile and Anatase. *Adv. Colloid Interface Sci.* **2002**, *99*, 255–264.

(66) Vakros, J.; Kordulis, C.; Lycourghiotis, A. Potentiometric Mass Titrations: A Quick Scan for Determining the Point of Zero Charge. *Chem. Commun.* **2002**, *17*, 1980–1981.

(67) Ahmad, M. A.; Prelot, B.; Dufour, F.; Durupthy, O.; Razafitianamaharavo, A.; Douillard, J. M.; Chaneac, C.; Villieras, F.; Zajac, J. Influence of Morphology and Crystallinity on Surface Reactivity of Nanosized Anatase TiO₂ Studied by Adsorption Techniques. 2. Solid–Liquid Interface. *J. Phys. Chem. C* **2013**, *117*, 4459–4469.

(68) Abidi, N.; Bonduelle-Skrzypczak, A.; Steinmann, S. N. Revisiting the Active Sites at the MoS₂/H₂O Interface via Grand-Canonical DFT: The Role of Water Dissociation. *ACS Appl. Mater. Interfaces* **2020**, *12*, 31401–31410.

(69) Gauthier, J. A.; Dickens, C. F.; Chen, L. D.; Doyle, A. D.; Nørskov, J. K. Solvation Effects for Oxygen Evolution Reaction Catalysis on IrO₂ (110). *J. Phys. Chem. C* **2017**, *121*, 11455–11463.

(70) Ko, K. C.; Bromley, S. T.; Lee, J. Y.; Illas, F. Size-Dependent Level Alignment between Rutile and Anatase TiO₂ Nanoparticles: Implications for Photocatalysis. *J. Phys. Chem. Lett.* **2017**, *8*, 5593–5598.

Recommended by ACS

Understanding the Effect of Single Atom Cationic Defect Sites in an Al₂O₃ (012) Surface on Altering Selenate and Sulfate Adsorption: An Ab Initio Study

Srishti Gupta, Christopher Muhich, *et al.*

MARCH 30, 2023

THE JOURNAL OF PHYSICAL CHEMISTRY C

READ 

Electrocatalytic Hydrogen Evolution at Full Atomic Utilization over ITO-Supported Sub-nano-Pt_n Clusters: High, Size-Dependent Activity Controlled by Fluxional Pt...

Simran Kumari, Philippe Sautet, *et al.*

MARCH 03, 2023

JOURNAL OF THE AMERICAN CHEMICAL SOCIETY

READ 

Oxygen Evolution at the BiVO₄-Water Interface: Mechanism of the Water Dehydrogenation Reaction

Sai Lyu, Alfredo Pasquarello, *et al.*

SEPTEMBER 12, 2022

ACS CATALYSIS

READ 

Interfacial Reactivity and Speciation Emerging from Na-Montmorillonite Interactions with Water and Formic Acid at 200 °C: Insights from Reactive Molecular Dynamics Simul...

Murali Gopal Muralaeddharan, Adri C. T. van Duin, *et al.*

APRIL 23, 2021

ACS EARTH AND SPACE CHEMISTRY

READ 

Get More Suggestions >